

## Durham Research Online

---

### Deposited in DRO:

16 February 2015

### Version of attached file:

Published Version

### Peer-review status of attached file:

Peer-reviewed

### Citation for published item:

Quinlan, R.A. and Bromley, E.H. and Pohl, E. (2015) 'A silk purse from a sow's ear – bioinspired materials based on -helical coiled coils.', *Current Opinion in Cell Biology*, 32 . pp. 131-137.

### Further information on publisher's website:

<http://dx.doi.org/10.1016/j.ceb.2014.12.010>

### Publisher's copyright statement:

© 2015 The Authors. Published by Elsevier Ltd. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/3.0/>).

### Additional information:

---

## Use policy

The full-text may be used and/or reproduced, and given to third parties in any format or medium, without prior permission or charge, for personal research or study, educational, or not-for-profit purposes provided that:

- a full bibliographic reference is made to the original source
- a [link](#) is made to the metadata record in DRO
- the full-text is not changed in any way

The full-text must not be sold in any format or medium without the formal permission of the copyright holders.

Please consult the [full DRO policy](#) for further details.



ELSEVIER

Available online at [www.sciencedirect.com](http://www.sciencedirect.com)

ScienceDirect

Current Opinion in  
Cell Biology

# A silk purse from a sow's ear — bioinspired materials based on $\alpha$ -helical coiled coils

Roy A Quinlan<sup>1,2</sup>, Elizabeth H Bromley<sup>2,3</sup> and Ehmke Pohl<sup>1,2,4</sup>

This past few years have heralded remarkable times for intermediate filaments with new revelations of their structural properties that has included the first crystallographic-based model of vimentin to build on the experimental data of intra-filament interactions determined by chemical cross-linking. Now with these and other advances on their assembly, their biomechanical and their cell biological properties outlined in this review, the exploitation of the biomechanical and structural properties of intermediate filaments, their nanocomposites and biomimetic derivatives in the biomedical and private sectors has started.

## Addresses

<sup>1</sup> School of Biological and Biomedical Sciences, The University of Durham, Stockton Road, Durham DH1 3LE, UK

<sup>2</sup> Biophysical Sciences Institute, The University of Durham, Stockton Road, Durham DH1 3LE, UK

<sup>3</sup> Department of Physics, The University of Durham, Stockton Road, Durham DH1 3LE, UK

<sup>4</sup> Department of Chemistry, The University of Durham, Stockton Road, Durham DH1 3LE, UK

Corresponding author: Quinlan, Roy A ([r.a.quinlan@dur.ac.uk](mailto:r.a.quinlan@dur.ac.uk))

Current Opinion in Cell Biology 2015, 32:xx–yy

This review comes from a themed issue on **Cell architecture**

Edited by **Sandrine Etienne-Manneville** and **Elly M Hol**

<http://dx.doi.org/10.1016/j.ceb.2014.12.010>

0955-0674/© 2015 The Authors. Published by Elsevier Ltd. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/3.0/>).

## Hard $\alpha$ -keratin — where it all began

It was through the study of  $\alpha$ -keratin that the first doyens of Structural Biology coined terms such as ' $\alpha$ -helix' [1] and then 'coiled coil' [2,3] to describe these fundamental features of protein structure. It has taken eight decades to solve most of the crystallographic detail of those first samples of hair and wool [4] and to appreciate the detail of the  $\alpha$ -keratin fibre and the precision of its oxidized state that underpins the resilience inherent to wool and hair fibres [5]. The importance of the pseudo-hexagonal packing of the  $\alpha$ -keratin fibres and how this contributes to the scaling (nanometre to millimetre) and composite potential of keratocyte  $\alpha$ -keratin materials is now realized [6<sup>•</sup>, 7<sup>•</sup>]. The molecular organization of wool makes it a wonderful textile as it exemplifies phase transition ( $\alpha$ -helix to  $\beta$ -sheet [8])

induced elasticity of its component keratin fibres when they are axially stretched [9]. This was first observed and documented by Astbury [4] and subsequently studied in more detail to reveal the importance of coiled-coil sliding and disulphide bonding to the biomechanical properties of hair [10,11]. The ability of hair to undergo a reversible phase transition [12,13] is an important feature to understand and then exploit in nanocomposite biomimetics (Figure 1). The nanocomposite alloy of nickel titanium is called a 'memory metal' because it can return to their original shape once the deforming forces are removed. Both hard  $\alpha$ -keratins [9] and cytoplasmic intermediate filaments [14] display such 'memory-like' properties too.


In hair, the biomechanical properties of the component intermediate filaments have been tuned to their local environment. So whilst the  $\alpha$ -helix to  $\beta$ -sheet phase transition of individual helices and coiled-coil sliding are key features for hard  $\alpha$ -keratins [10], the amorphous matrix into which they are embedded [15<sup>••</sup>] and the cell matrix complex [16] play their part. The matrix shields the embedded  $\alpha$ -keratin fibres from water, which for wool and hair is critical as their  $\alpha$ -keratin stretches easier when it is wet than when it is dry [17].

At the other extreme, is hagfish slime. This provides a protective slime coat that is secreted by these animals when threatened or attacked. Intermediate filament-based fibres are the main structural component. The secrets of the assembly, storage and subsequent deployment of the hagfish slime filaments are now under investigation [18<sup>••</sup>]. Yet more attractive features to incorporate into future intermediate filament-based fibres and nanocomposite materials are being revealed.

It is the inherent biomechanical properties of such  $\alpha$ -helical coiled coil fibres and the atomic detail of their  $\alpha$ -helix, coiled coil and higher order (e.g. pseudo-hexagonal in hair) packing and organization that provide blueprints for the next generation of bioengineered fibre materials (Figure 1). Whilst the structural determination of some (e.g. keratin) might remain incomplete [19], we can still appreciate the scaling (nm to mm) potential of the fibre-matrix interaction [6<sup>••</sup>] to generate high tensile strength fibres. Indeed, it is the irregular fibre packing into the macrofibrils found in hard  $\alpha$ -keratin materials that has so far resisted the conventional crystallographic interrogation to reveal the detail of this scaling potential and its diversity within keratin-based materials. This tertiary

## 2 Cell architecture

Figure 1

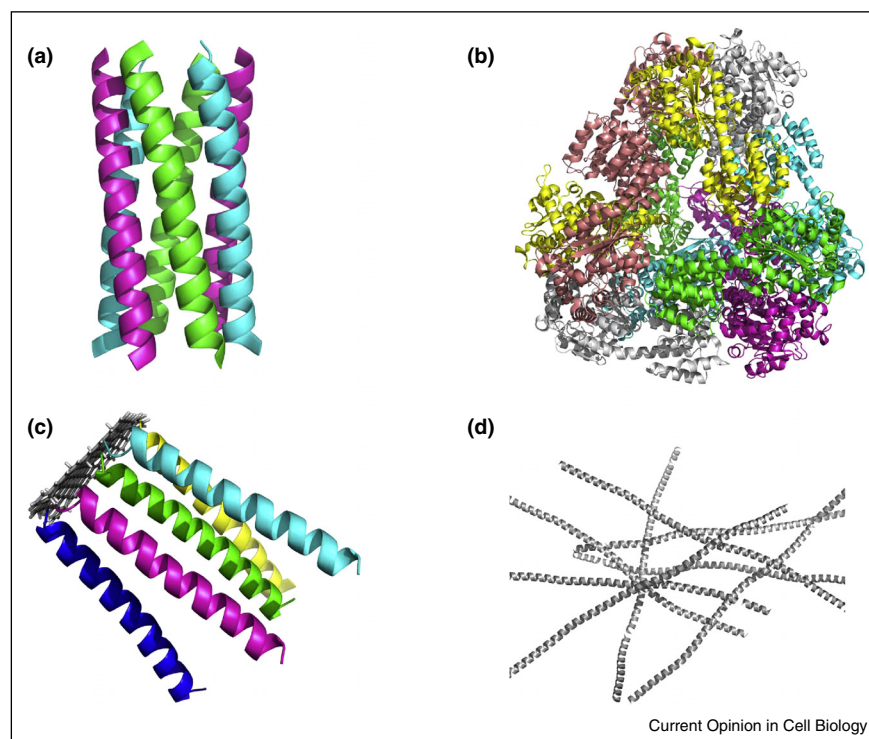

Current and future directions of peptide coils design. **(a)** Crystal structure of the *de novo* designed parallel coiled-coil hexamer (pdb code 3R3K [64]); **(b)** crystal structure of a *de novo* designed 16 nm protein cage (pdb code 4D9J [90]); **(c)** model of designed peptide coils covalently attached to graphene sheet(s) as an example of a potential nanocomposite; **(d)** model of macroscopic structures built from peptide chains.

organization of intermediate filaments is one of the mesoscopic features that we understand the least, but which will be critical to their successful exploitation in future bioengineered nanocomposite materials (Figure 1).

### The science of storing coiled coils and weaving threads with the tensile strength of steel

Weight for weight, spider silk is one of the strongest fibres on the planet — stronger even than steel. If intermediate filaments and their biomimetics are to become commercial alternatives, they will need to be similarly strong. Some coiled-coil protein fibres can accommodate very high elastic strains (e.g. hagfish slime fibres [20]) and when confronted with high deforming forces, transform from  $\alpha$ -helical rich structures into rigid  $\beta$ -sheets that are then locked to exhibit failure stresses approaching that of natural silk [20]. The recent analysis of silk proteins from bees, ants and hornets has found them to be coiled-coil based. They illustrate that we have still much to learn about coiled coil and their potential as materials of the future [21]. These silks are woven on demand by the insects forming either fibres or sheets [22]. Making threads from recombinant intermediate filament proteins

is more challenging [23,24<sup>••</sup>]. Generating recombinant silks [25] is already a multibillion pound, global industry because of the wide range of desirable properties associated with such fibres and a shortage of spiders with a strong work ethic!

A bioelastomeric fibre made recombinantly and to specific mechanical, dye uptake, hydration compatible properties are highly desirable features for the textile industry. If such properties could then also be coupled to the storage and weaving of these materials as observed in nature then this would revolutionize yarn production and storage. Imagine being able to form *de novo* fibres on demand from a pool of 40  $\mu$ m tactoids or 1  $\mu$ m birefringent rods as seen for the silks of different *Apoidea* and *Vespoidea* species (see [22] and references therein). Imagine storing pre-woven, untangled skeins as in the hagfish slime thread gland [18<sup>••</sup>]. The storage, spinning and curing of the coiled-coil fibres achieved in the natural world is a reality far beyond the structural biologist's panacea for dealing with intermediate filament coiled coils — urea and then more urea and guanidinium hydrochloride! To understand the extent of the universe for natural intermediate filaments, we need

to understand how fibres are ‘cured’ during their assembly, the mechanisms of their strain-induced conformational changes at the molecular scale and the origin of the internal energy dissipation. Armed with such properties, the future textile, medical and defense industries will be unrecognizable!

### Human hair – a shape memory material with ancient origins

For each of us, hair is a daily reminder of the importance of  $\alpha$ -keratin-based fibres and it is also a signature for future archaeologists [26<sup>•</sup>]. The interconversion of straight and curly hair is a cosmetic decision for which the mechanistic and cell biological details are now becoming clearer. The matrix proteins that embed the  $\alpha$ -keratin fibres are critical for such cosmetic changes [27] with the inter-matrix S–S oxidation of these proteins and not the keratins determining the degree of curl. Curly hair is independent of ethnicity and due to the asymmetric differentiation of the precortex in the human hair shaft as a result of differences in cell proliferation, but the extent of the curliness seems to be due to the  $\alpha$ -keratin content [28]. We can perhaps add ‘memory material’ as a feature to the dynamic nanocomposite property of human hair.

There are 24 different keratins expressed in those cells making the human beard [29<sup>••</sup>] and, considering the functional unit of both epidermal and hard  $\alpha$ -keratins are tetramers [30,31], we have yet to determine whether fidelity or promiscuity [32] in  $\alpha$ -keratin pairing are mutual exclusive or tolerated within the hair fibres [29<sup>••</sup>]. Hair  $\alpha$ -keratins themselves have ancient origins as revealed by analysis of the Neanderthal genome and its relationship to present day humans [33<sup>•</sup>,34<sup>•</sup>]. Four hair  $\alpha$ -keratin genes with an unusually high frequency of introgression were found in East Asians (KRT83, KRT84, KRT85, KRT86) whilst those with high frequency in Europeans (KRT5, KRT71, KRT74) were three completely different genes of epithelial keratin (KRT5) or without annotated function [34<sup>•</sup>]. From these studies on humanoid evolution, it is the thermoregulatory and protective properties of hair that is considered to be an important property. It is also clear the resilience of hair and its proteins are critical, a point illustrated by the fact that storage for 30 000 years in the Siberian permafrost did nothing to dent the *in vitro* assembly potential of mammoth hair  $\alpha$ -keratins [35]. This resilience affords hard  $\alpha$ -keratins a role as a forensic/drug abuse/diet sensor (e.g. [36<sup>•</sup>,37]). Tracking modern carbon in tusks [38] and verifying shahtoosh products [39] absolutely depends upon the resilience of hair.

### Intermediate filament coiled coils and their current applications in biomedicine

Our discussion has so far focused our attention onto the materials industry, but the application of the underlying knowledge of intermediate filament, coiled coil assembly

has already been exploited in biomedicine as a self-assembly nanoparticle delivery platform. These applications would not have been realized without the following intellectual framework. Crystallographic data for vimentin, keratin and lamin proteins [19,40<sup>••</sup>,41], combined with chemical cross-linking [42,43] and biophysical characterization of the assembly units [31,44], the importance of trigger sequences [45] and the design of stable coiled coil peptides [46] were the knowledge base needed to design trimeric and pentameric coiled coil nanoparticles [47]. Such particles now function as a vaccine scaffold [48]. The self-assembly polypeptide nanoparticle (SAPN) strategy has other guises (e.g. synthetic virus-like particle; SVLP) and derivations such as lipoprotein virus-like particles [49] and coiled coil based vesicles with membrane fusion properties [50<sup>••</sup>]. Using such technologies, vaccines to malaria [51,52], toxoplasma [53] and HIV [54] are being developed, but the technology is also a useful scientific tool to target specific epitopes in any protein of interest e.g. Schroeder et al. [55]. It is also clear though that such virus-like structures can be used to target specific cells [56<sup>••</sup>] and also deliver cargo, as evidenced by the proof principle experiment of encapsulating gold particles within these structures [57] to expand their biomedical application [58].

It is the potential of the coiled coil and its ordered oligomerisation that is inspirational to bioengineers as evidenced by the analysis of the GCN4 coiled coil [59<sup>•</sup>,60]. There are several aspects to the oligomerization that might be controlled including the binding affinity, oligomerization state (dimer, trimer, tetramer, etc.), the direction of association of sequences (parallel versus anti-parallel) and the partnering specificity. Control of binding affinity can be achieved via sequence length and has been explicitly demonstrated in dimeric coiled coils [61]. Dimer, trimer or tetramer coiled coils can be designed [62<sup>••</sup>], but their ability to sort within a mixture is still missing. Design of  $\alpha$ -barrels with central channels formed from (parallel) coiled coils extent the potential applications [63] on the back of the discovery of the CC-hex state for a synthetic coiled coil [64]. Anti-parallel coiled coils have also been investigated [65], culminating in a tetrahedron built from a single polypeptide chain because the designed peptide specified both parallel and anti-parallel coiled coils [66]. Finally the analysis of partner specificity of parallel dimeric coiled coils [67,68] resulted in algorithms to predict the interaction strength of *de novo* sequences [69,70]. Now sequences that assemble in defined partnerships [71] to produce specified small nanostructures are available [72].

### Bioinspired filaments based on coiled coils – deciphering the scaling features of intermediate filaments for application in the materials of the future

The complex mechanical properties of intermediate filaments [14], including their ability to form filaments of

#### 4 Cell architecture

defined width, their ability to exhibit visco-elasticity and strain hardening and their ability to respond to deformation in a dynamic and environmentally sensitive fashion are a challenge to replicate in bioengineered mimetics. Knowledge of the coiled coil building block, the heptad repeat with its hydrophobic seam and knobs-into-holes packing [3] and the surface charge repeat that drives oligomerization [59,60] have allowed the first attempts at the manufacture of bioinspired filaments. These attempts included the Self-Assembly Filaments (SAFs) that utilize the keratin heterodimer principle [73], and helped identify the importance of the scaling problem [74]. The synthetic filaments formed were rigid with variable width and length, a far cry from the uniformity of the cytoplasmic intermediate filament. Progress is being made and the recent iteration illustrates that refinement of the original 28mer polypeptide can deliver 80 nm wide 40  $\mu$ m long fibres [75]. For these engineered filaments and the intermediate filament proteins themselves [40\*\*], it is atomic level structural information of the coiled coil packing within the polymer that is required to understand the self-assembly features. Using coiled coil domains from other structural proteins (coiled-coil domain of cartilage oligomeric matrix protein [76] or by design [77] pH or small molecule induced fibre assemblies are possible and seem capable of forming microfibrils [76] therefore demonstrating the nano-scaling to meso-scaling property required for future biomimetics of, for instance, wool or silk.

### Conclusions

The current state of the art regarding designed coiled coil filament assemblies can be summarized as follows. Successful programming of the behavior of individual building blocks permits controlled self-assembly at the nanometre scale. Width and radius can be controlled by the length of the assembly subunit, but subsequent hierarchical assembly for example [74–76] remains an emergent property that is poorly understood and, as length scales increase, the synthesis of specific microstructures is unpredictable. This matches the information known from natural systems in which the specifics at the nano-scale are often well characterized by the connection to the primary sequence whilst the detail of the metre-scale microstructure is not. The challenge therefore, for structural cell biologists and bioengineers is to understand the principles that afford the width, length and subcellular organisation of intermediate filaments.

It is the length scale spanning nanocomposite nature of intermediate filament-based materials [6\*\*,7\*\*] that is responsible for their remarkable mechanical properties [9]. In living cells too intermediate filaments are key determinants of the cellular mechanical properties for example [78] and their networks proposed to be flaw tolerant [79], but they are also integral to the cellular stress response [80,81]. The dynamic nature of intermediate filaments and the role of post-translational modifications in facilitating their subcellular organization and

their different functions underline the importance of their assembly and subunit dynamics to their cellular functions [82]. We must also appreciate their links to membranes and other cellular structures, whether it is the attachment of the nuclear lamina to the inner nuclear membrane for example [83] or the attachment of cytoplasmic filaments to the outer nuclear membrane for example [84] or to the plasma membrane and other membrane compartments within the cell for example [85,86], all are crucial to their biomechanical function and are further examples of their nanocomposite potential. These properties are conserved throughout evolution, with bacteria such as *Streptomyces* also utilizing intermediate filament-like proteins to strengthen hyphal membranes. The bacterial intermediate filament-like protein FIIP forms a fibrous mesh to support vulnerable points on the plasma membrane [87], electron microscope images that fire the imagination and resonate with those iconic pictures of the oocyte nuclear lamina [88]. Whilst there is currently a large gap between the functionality of synthetic and natural fibres, bioengineered nanocomposites [89] that can sense and transduce mechanical and environmental cues to produce transcriptional and translational responses [82] is a technological prize awaiting our full appreciation and application as a result of exploiting fully the meso-scale properties of intermediate filaments and their bioengineered mimics.

### Acknowledgements

The financial support of the Leverhulme Trust (RPG-2012-554 (RAQ)), Fight for Sight (#1358 (RAQ)), BBSRC (BB/L014092/1 (RAQ); BB/K00817X/1 (EP)) and EPSRC (EP/1010173/1) are gratefully acknowledged.

### References and recommended reading

Papers of particular interest, published within the period of review, have been highlighted as:

- of special interest
- of outstanding interest

1. Pauling L, Corey RB: **Compound helical configurations of polypeptide chains: structure of proteins of the  $\alpha$ -keratin type.** *Nature* 1953, **171**:59–61.
2. Crick FH: **Is alpha-keratin a coiled coil?** *Nature* 1952, **170**:882–883.
3. Crick FHC: **The packing of  $\alpha$ -helices: simple coiled-coil.** *Acta Crystallogr* 1953, **6**:689–697.
4. Astbury WT, Woods HJ: **X-ray studies of the structures of hair, wool and related fibres. II. The molecular structure and elastic properties of hair keratin.** *Trans R Soc Lond* 1934, **A232**: 333–394.
5. Bruce Fraser RD, Parry DA: **The role of disulfide bond formation in the structural transition observed in the intermediate filaments of developing hair.** *J Struct Biol* 2012, **180**:117–124.
6. Fortier P, Suei S, Kreplak L: **Nanoscale strain-hardening of keratin fibres.** *PLoS ONE* 2012, **7**:e41814.
7. Harland DP, Walls RJ, Vernon JA, Dyer JM, Woods JL, Bell F: **Three-dimensional architecture of macrofibrils in the human scalp hair cortex.** *J Struct Biol* 2014, **185**:397–404.

A comprehensive sdescription of the hair nanocomposite and its component parts.



8. Bendit EG: **The [alpha]-[beta] transformation in keratin.** *Nature* 1957, **179**:4558-5535.
9. Miserez A, Guerette PA: **Phase transition-induced elasticity of alpha-helical bioelastomeric fibres and networks.** *Chem Soc Rev* 2013, **42**:1973-1995.
10. Kreplak L, Franbourg A, Briki F, Leroy F, Dalle D, Doucet J: **A new deformation model of hard alpha-keratin fibers at the nanometer scale: implications for hard alpha-keratin intermediate filament mechanical properties.** *Biophys J* 2002, **82**:2265-2274.
11. Chou CC, Buehler MJ: **Structure and mechanical properties of human trichocyte keratin intermediate filament protein.** *Biomacromolecules* 2012, **13**:3522-3532.
12. Dobb MG, Johnston FR, Nott JA, Oster L, Sikorski J, Simpson WS: **12 – Morphology of the cuticle layer in wool fibres and other animal hairs.** *J Text Inst Trans* 1961, **52**:T153-T170.
13. Meyers MA, Chen P-Y, Lin A-Y-M, Seki Y: **Biological materials: structure and mechanical properties.** *Prog Mater Sci* 2008, **53**:1-206.
14. Janmey PA, Euteneuer U, Traub P, Schliwa M: **Viscoelastic properties of vimentin compared with other filamentous biopolymer networks.** *J Cell Biol* 1991, **113**:155-160.
15. Greenberg DA, Fudge DS: **Regulation of hard alpha-keratin mechanics via control of intermediate filament hydration: matrix squeeze revisited.** *Proc Biol Sci* 2013, **280**:20122158.
- The importance of restricting the hydration of hard  $\alpha$ -keratins to their mechanical properties.
16. Harland DP, Caldwell JP, Woods JL, Walls RJ, Bryson WG: **Arrangement of trichokeratin intermediate filaments and matrix in the cortex of Merino wool.** *J Struct Biol* 2011, **173**:29-37.
17. Fudge DS, Gosline JM: **Molecular design of the alpha-keratin composite: insights from a matrix-free model, hagfish slime threads.** *Proc Biol Sci* 2004, **271**:291-299.
18. Winegard T, Herr J, Mena C, Lee B, Dinov I, Bird D *et al.*: **Coiling and maturation of a high-performance fibre in hagfish slime gland thread cells.** *Nat Commun* 2014, **5**:3534.
- The opposite to hair regarding water — functional intermediate filaments within an aqueous environment; different mechanical properties dictated by the local environment, but still these filament perform.
19. Lee CH, Kim MS, Chung BM, Leahy DJ, Coulombe PA: **Structural basis for heteromeric assembly and perinuclear organization of keratin filaments.** *Nat Struct Mol Biol* 2012, **19**:707-715.
20. Fudge DS, Hillis S, Levy N, Gosline JM: **Hagfish slime threads as a biomimetic model for high performance protein fibres.** *Bioinspir Biomim* 2010, **5**:035002.
21. Poole J, Church JS, Woodhead AL, Huson MG, Sriskantha A, Kyrtzlis IL *et al.*: **Continuous production of flexible fibers from transgenically produced honeybee silk proteins.** *Macromol Biosci* 2013, **13**:1321-1326.
22. Sutherland TD, Weisman S, Walker AA, Mudie ST: **Invited review the coiled coil silk of bees, ants, and hornets.** *Biopolymers* 2012, **97**:446-454.
23. Negishi A, Armstrong CL, Kreplak L, Rheinstadter MC, Lim LT, Gillis TE *et al.*: **The production of fibers and films from solubilized hagfish slime thread proteins.** *Biomacromolecules* 2012, **13**:3475-3482.
24. Pinto N, Yang FC, Negishi A, Rheinstadter MC, Gillis TE, Fudge DS: **Self-assembly enhances the strength of fibers made from vimentin intermediate filament proteins.** *Biomacromolecules* 2014, **15**:574-581.
- The first threads spun from vimentin, a cytoplasmic, cellular intermediate filament.
25. Schacht K, Scheibel T: **Processing of recombinant spider silk proteins into tailor-made materials for biomaterials applications.** *Curr Opin Biotechnol* 2014, **29**:62-69.
26. Matsunaga R, Abe R, Ishii D, Watanabe S, Kiyoshi M, Nocker B *et al.*: **Bidirectional binding property of high glycine-tyrosine keratin-associated protein contributes to the mechanical strength and shape of hair.** *J Struct Biol* 2013, **183**:484-494.
- It is not all hard  $\alpha$ -keratins — the contribution of the keratin associated proteins to the mechanical properties and features of hair.
27. Suzuta K, Ogawa S, Takeda Y, Kaneyama K, Arai K: **Intermolecular disulfide cross-linked structural change induced by permanent wave treatment of human hair with thioglycolic acid.** *J Cosmet Sci* 2012, **63**:177-196.
28. Thibaut S, Barbarat P, Leroy F, Bernard BA: **Human hair keratin network and curvature.** *Int J Dermatol* 2007, **46**(Suppl 1):7-10.
29. Langbein L, Yoshida H, Praetzel-Wunder S, Parry DA, Schweizer J: **• The keratins of the human beard hair medulla: the riddle in the middle.** *J Invest Dermatol* 2010, **130**:55-73.
- The best comprehensive study on human hard  $\alpha$ -keratins.
30. Woods EF, Gruen LC: **Structural studies on the microfibrillar proteins of wool: characterization of the  $\alpha$ -helix-rich particle produced by chymotryptic digestion.** *Aust J Bio Sci* 1981, **34**:515-526.
31. Quinlan RA, Cohlberg JA, Schiller DL, Hatzfeld M, Franke WW: **Heterotypic tetramer (A2D2) complexes of non-epidermal keratins isolated from cytoskeletons of rat hepatocytes and hepatoma cells.** *J Mol Biol* 1984, **178**:365-388.
32. Langbein L, Eckhart L, Rogers MA, Praetzel-Wunder S, Schweizer J: **Against the rules: human keratin K80: two functional alternative splice variants, K80 and K80.1, with special cellular localization in a wide range of epithelia.** *J Biol Chem* 2010, **285**:36909-36921.
33. Vernot B, Akey JM: **Resurrecting surviving Neandertal lineages from modern human genomes.** *Science* 2014, **343**:1017-1021.
- The value of hard  $\alpha$ -keratins to human ancestry.
34. Sankararaman S, Mallick S, Dannemann M, Prüfer K, Kelso J, Paabo S *et al.*: **The genomic landscape of Neanderthal ancestry in present-day humans.** *Nature* 2014, **507**:354-357.
- Evolution of human hair  $\alpha$ -keratins.
35. Gillespie JM: **Mammoth hair: stability of alpha-keratin structure and constituent proteins.** *Science* 1970, **170**:1100-1102.
36. Fahy GE, Richards M, Riedel J, Hublin JJ, Boesch C: **Stable isotope evidence of meat eating hunting specialization in adult male chimpanzees.** *Proc Natl Acad Sci U S A* 2013, **110**:5829-5833.
- Hair resilience and an example of how it has forensic, dietary and regulatory applications.
37. Gambelunghe C, Rossi R, Ferranti C, Rossi R, Bacci M: **Hair analysis by GC/MS/MS to verify abuse of drugs.** *J Appl Toxicol* 2005, **25**:205-211.
38. Uno KT, Quade J, Fisher DC, Wittemyer G, Douglas-Hamilton I, Andanje S *et al.*: **Bomb-curve radiocarbon measurement of recent biologic tissues and applications to wildlife forensics and stable isotope (paleo)ecology.** *Proc Natl Acad Sci U S A* 2013, **110**:11736-11741.
39. Fei J, Yang J, Zhou H, Tang M, Lu W, Yan A *et al.*: **A novel method for identifying shahtoosh.** *J Forensic Sci* 2014, **59**:723-728.
40. Chernyatina AA, Nicolet S, Aebi U, Herrmann H, Strelkov SV: **• Atomic structure of the vimentin central alpha-helical domain and its implications for intermediate filament assembly.** *Proc Natl Acad Sci U S A* 2012, **109**:13620-13625.
- First crystallographic model of the complete vimentin coiled coil.
41. Strelkov SV, Schumacher J, Burkhard P, Aebi U, Herrmann H: **Crystal structure of the human lamin A coil 2B dimer: implications for the head-to-tail association of nuclear lamins.** *J Mol Biol* 2004, **343**:1067-1080.
42. Steinert PM, Marekov LN, Fraser RD, Parry DA: **Keratin intermediate filament structure. Crosslinking studies yield quantitative information on molecular dimensions and mechanism of assembly.** *J Mol Biol* 1993, **230**:436-452.
43. Wang H, Parry DA, Jones LN, Idler WW, Marekov LN, Steinert PM: **In vitro assembly and structure of trichocyte keratin intermediate filaments: a novel role for stabilization by disulfide bonding.** *J Cell Biol* 2000, **151**:1459-1468.

## 6 Cell architecture

44. Quinlan RA, Hatzfeld M, Franke WW, Lustig A, Schulthess T, Engel J: **Characterization of dimer subunits of intermediate filament proteins.** *J Mol Biol* 1986, **192**:337-349.
  45. Wu KC, Bryan JT, Morasso MI, Jang SI, Lee JH, Yang JM *et al.*: **Coiled-coil trigger motifs in the 1B and 2B rod domain segments are required for the stability of keratin intermediate filaments.** *Mol Biol Cell* 2000, **11**:3539-3558.
  46. Burkhard P, Ivaninskii S, Lustig A: **Improving coiled-coil stability by optimizing ionic interactions.** *J Mol Biol* 2002, **318**:901-910.
  47. Raman S, Machaidze G, Lustig A, Aebi U, Burkhard P: **Structure-based design of peptides that self-assemble into regular polyhedral nanoparticles.** *Nanomedicine* 2006, **2**:95-102.
  48. Yang Y, Ringler P, Muller SA, Burkhard P: **Optimizing the refolding conditions of self-assembling polypeptide nanoparticles that serve as repetitive antigen display systems.** *J Struct Biol* 2012, **177**:168-176.
  49. Ghasparian A, Riedel T, Koomullil J, Moehle K, Gorba C, Svergun DI *et al.*: **Engineered synthetic virus-like particles and their use in vaccine delivery.** *Chembiochem: a European journal of chemical biology.* 2011, **12**:100-109.
  50. Rabe M, Schwieger C, Zope HR, Versluis F, Kros A: **Membrane interactions of fusogenic coiled-coil peptides: implications for lipopeptide mediated vesicle fusion.** *Langmuir* 2014, **30**:7724-7735.
- Targetted cargo delivery with membrane fusion — one of the potential derivations of the coiled coil based nanoparticle.
51. Kaba SA, Brando C, Guo Q, Mittelholzer C, Raman S, Tropel D *et al.*: **A nonadjuvanted polypeptide nanoparticle vaccine confers long-lasting protection against rodent malaria.** *J Immunol* 2009, **183**:7268-7277.
  52. Mueller MS, Renard A, Boato F, Vogel D, Naegeli M, Zurbriggen R *et al.*: **Induction of parasite growth-inhibitory antibodies by a virosomal formulation of a peptidomimetic of loop I from domain III of *Plasmodium falciparum* apical membrane antigen 1.** *Infect Immun* 2003, **71**:4749-4758.
  53. El Bissati K, Zhou Y, Dasgupta D, Cobb D, Dubey JP, Burkhard P *et al.*: **Effectiveness of a novel immunogenic nanoparticle platform for *Toxoplasma* peptide vaccine in HLA transgenic mice.** *Vaccine* 2014, **32**:3243-3248.
  54. Wahome N, Pfeiffer T, Ambiel I, Yang Y, Keppler OT, Bosch V *et al.*: **Conformation-specific display of 4E10 and 2F5 epitopes on self-assembling protein nanoparticles as a potential HIV vaccine.** *Chem Biol Drug Des* 2012, **80**:349-357.
  55. Schroeder U, Graff A, Buchmeier S, Rigler P, Silvan U, Tropel D, Jockusch BM, Aebi U, Burkhard P, Schoenenberger CA: **Peptide nanoparticles serve as a powerful platform for the immunogenic display of poorly antigenic actin determinants.** *J Mol Biol* 2009, **386**:1368-1381 <http://dx.doi.org/10.1016/j.jmb.2008.11.023>.
  56. Yang Y, Neef T, Mittelholzer C, Garcia Garayoa E, Blauenstein P, Schibli R *et al.*: **The biodistribution of self-assembling protein nanoparticles shows they are promising vaccine platforms.** *J Nanobiotechnol* 2013, **11**:36.
- Coiled coil based nanoparticles and their application in vaccine development. An excellent paper detailing progress with this application of coiled coils and entry point into the affiliated literature.
57. Yang Y, Burkhard P: **Encapsulation of gold nanoparticles into self-assembling protein nanoparticles.** *J Nanobiotechnol* 2012, **10**:42.
  58. Doll TA, Raman S, Dey R, Burkhard P: **Nanoscale assemblies and their biomedical applications.** *J R Soc Interface* 2013, **10**:20120740.
  59. Harbury PB, Kim PS, Alber T: **Crystal structure of an isoleucine-zipper trimer.** *Nature* 1994, **371**:80-83.  
A seminal work for coiled coils.
  60. Harbury PB, Zhang T, Kim PS, Alber T: **A switch between two-, three-, and four-stranded coiled coils in GCN4 leucine zipper mutants.** *Science* 1993, **262**:1401-1407.
  61. Thomas F, Boyle AL, Burton AJ, Woolfson DN: **A set of de novo designed parallel heterodimeric coiled coils with quantified dissociation constants in the micromolar to sub-nanomolar regime.** *J Am Chem Soc* 2013, **135**:5161-5166.
  62. Fletcher JM, Harniman RL, Barnes FR, Boyle AL, Collins A, Mantell J *et al.*: **Self-assembling cages from coiled-coil peptide modules.** *Science* 2013, **340**:595-599.
- Nanoparticles design.
63. Woolfson DN, Bartlett GJ, Bruning M, Thomson AR: **New currency for old rope: from coiled-coil assemblies to alpha-helical barrels.** *Curr Opin Struct Biol* 2012, **22**:432-441.
  64. Zaccai NR, Chi B, Thomson AR, Boyle AL, Bartlett GJ, Bruning M *et al.*: **A de novo peptide hexamer with a mutable channel.** *Nat Chem Biol* 2011, **7**:935-941.
  65. Hadley EB, Gellman SH: **An antiparallel alpha-helical coiled-coil model system for rapid assessment of side-chain recognition at the hydrophobic interface.** *J Am Chem Soc* 2006, **128**:16444-16445.
  66. Gradisar H, Bozic S, Doles T, Vengust D, Hafner-Bratkovic I, Mertelj A *et al.*: **Design of a single-chain polypeptide tetrahedron assembled from coiled-coil segments.** *Nat Chem Biol* 2013, **9**:362-366.
  67. Acharya A, Rishi V, Vinson C: **Stability of 100 homo and heterotypic coiled-coil a-a' pairs for ten amino acids (A, L, I, V, N, K, S, T, E, and R).** *Biochemistry* 2006, **45**:1132-1232.
  68. Newman JR, Keating AE: **Comprehensive identification of human bZIP interactions with coiled-coil arrays.** *Science* 2003, **300**:2097-2101.
  69. Mason JM, Schmitz MA, Muller KM, Arndt KM: **Semirational design of Jun-Fos coiled coils with increased affinity: universal implications for leucine zipper prediction and design.** *Proc Natl Acad Sci U S A* 2006, **103**:8989-8994.
  70. Negron C, Keating AE: **Multistate protein design using CLEVER and CLASSY.** *Methods Enzymol* 2013, **523**:171-190.
  71. Reinke AW, Grant RA, Keating AE: **A synthetic coiled-coil interactome provides heterospecific modules for molecular engineering.** *J Am Chem Soc* 2010, **132**:6025-6031.
  72. Bromley EH, Sessions RB, Thomson AR, Woolfson DN: **Designed alpha-helical tectons for constructing multicomponent synthetic biological systems.** *J Am Chem Soc* 2009, **131**:928-930.
  73. Pandya MJ, Spooner GM, Sunde M, Thorpe JR, Rodger A, Woolfson DN: **Sticky-end assembly of a designed peptide fiber provides insight into protein fibrillogenesis.** *Biochemistry* 2000, **39**:8728-8734.
  74. Bromley EH, Channon KJ, King PJ, Mahmoud ZN, Banwell EF, Butler MF *et al.*: **Assembly pathway of a designed alpha-helical protein fiber.** *Biophys J* 2010, **98**:1668-1676.
  75. Sharp TH, Bruning M, Mantell J, Sessions RB, Thomson AR, Zaccai NR *et al.*: **Cryo-transmission electron microscopy structure of a gigadalton peptide fiber of de novo design.** *Proc Natl Acad Sci U S A* 2012, **109**:13266-13271.
  76. Hume J, Sun J, Jacquet R, Renfrew PD, Martin JA, Bonneau R *et al.*: **Engineered coiled-coil protein microfibers.** *Biomacromolecules* 2014, **15**:3503-3510.
  77. Potekhin SA, Melnik TN, Popov V, Lanina NF, Vazina AA, Rigler P *et al.*: **De novo design of fibrils made of short alpha-helical coiled coil peptides.** *Chem Biol* 2001, **8**:1025-1032.
  78. Guo M, Ehrlicher AJ, Mahammad S, Fabich H, Jensen MH, Moore JR *et al.*: **The role of vimentin intermediate filaments in cortical and cytoplasmic mechanics.** *Biophys J* 2013, **105**:1562-1568.
  79. Qin Z, Buehler MJ: **Flaw tolerance of nuclear intermediate filament lamina under extreme mechanical deformation.** *ACS Nano* 2011, **5**:3034-3042.
  80. Toivola DM, Strnad P, Habtezion A, Omary MB: **Intermediate filaments take the heat as stress proteins.** *Trends Cell Biol* 2010, **20**:79-91.

81. Landsbury A, Perng MD, Pohl E, Quinlan RA: In *Functional Symbiosis Between the Intermediate Filament Cytoskeleton and Small Heat Shock Proteins*. Edited by Simon S, Arrigo AP. 2010:55-87.
82. Snider NT, Omary MB: **Post-translational modifications of intermediate filament proteins: mechanisms and functions**. *Nat Rev Mol Cell Biol* 2014, **15**:163-177.
83. Swift J, Discher DE: **The nuclear lamina is mechano-responsive to ECM elasticity in mature tissue**. *J Cell Sci* 2014, **127**(Pt 14):3005-3015.
84. Chapman MA, Zhang J, Banerjee I, Guo LT, Zhang Z, Shelton GD *et al.*: **Disruption of both nesprin 1 and desmin results in nuclear anchorage defects and fibrosis in skeletal muscle**. *Hum Mol Genet* 2014, **23**:5879-5892.
85. Clemen CS, Herrmann H, Strelkov SV, Schroder R: **Desminopathies: pathology and mechanisms**. *Acta Neuropathol* 2013, **125**:47-75.
86. Konieczny P, Fuchs P, Reipert S, Kunz WS, Zeold A, Fischer I *et al.*: **Myofiber integrity depends on desmin network targeting to Z-disks and costameres via distinct plectin isoforms**. *J Cell Biol* 2008, **181**:667-681.
87. Fuchino K, Bagchi S, Cantlay S, Sandblad L, Wu D, Bergman J *et al.*: **Dynamic gradients of an intermediate filament-like cytoskeleton are recruited by a polarity landmark during apical growth**. *Proc Natl Acad Sci U S A* 2013, **110**:E1889-E1897.
88. Aebi U, Cohn J, Buhle L, Gerace L: **The nuclear lamina is a meshwork of intermediate-type filaments**. *Nature* 1986, **323**:560-564.
89. Guerette PA, Hoon S, Seow Y, Raida M, Masic A, Wong FT *et al.*: **Accelerating the design of biomimetic materials by integrating RNA-seq with proteomics and materials science**. *Nat Biotechnol* 2013, **31**:908-915.
90. Lai YT, Cascio D, Yeates TO: **Structure of a 16-nm cage designed by using protein oligomers**. *Science* 2012, **336**:1129.